

# Note on the determination of Characteristic Value of Observations

by Ervin Poulsen, 2001-02-03  
supplied: 2001-02-18

According to the EN 1504-standards, the Eurocode prEN 1992-1-1, 'Eurocode 2 Design of concrete structures part 1: general rules and rules for buildings', and EN 206-1 the lower characteristic value shall be the 5 % fractile and the upper characteristic value shall be the 95 % fractile.

In order to determine the characteristic value of observations obtained from testing concrete or similar materials it is convenient to make the following assumptions:

- The lower characteristic value is defined as the 5 % fractile.
- The upper characteristic value is defined as the 95 % fractile.
- The characteristic value shall be determined from observations at a level of confidence of  $\alpha = 84.1$  %.
- The observations from the testing are assumed statistically to be logarithmic normally distributed.
- The coefficient of variation is unknown.

In the case of  $n \geq 3$  observations (e.g. strengths) from one single section of inspection, calculation of the characteristic value of the following observations:

$$f_1, f_2, f_3, \dots, f_n \tag{1}$$

are carried out as follows: first the mean value  $M_{\ln f}$  and the standard deviation  $S_{\ln f}$  of the Napir logarithm of the observations (1), i.e. the values:

$$\ln f_1, \ln f_2, \ln f_3, \dots, \ln f_n \tag{2}$$

are carried out. The easiest way is to apply a spreadsheet, e.g. Excel, cf. example 1. Then the lower characteristic value (5 % fractile) is:

$$f_{kl} = \exp(M_{\ln f} - k_n \cdot S_{\ln f}) \tag{3}$$

and the upper characteristic value (95 % fractile) is:

$$f_{ku} = \exp(M_{\ln f} + k_n \cdot S_{\ln f}) \tag{4}$$

The factor  $k_n$  is based upon the non-central  $t$ -distribution and obeys the values shown in Table 1:

$n$	3	4	5	6	7	8	9	10	11	12	15	20	30	50	100
$k_n$	4.11	3.28	2.91	2.70	2.57	2.47	2.40	2.34	2.29	2.25	2.16	2.07	1.98	1.89	1.81

Table 1. Values of the factor  $k_n$  in equation (3) and (4).

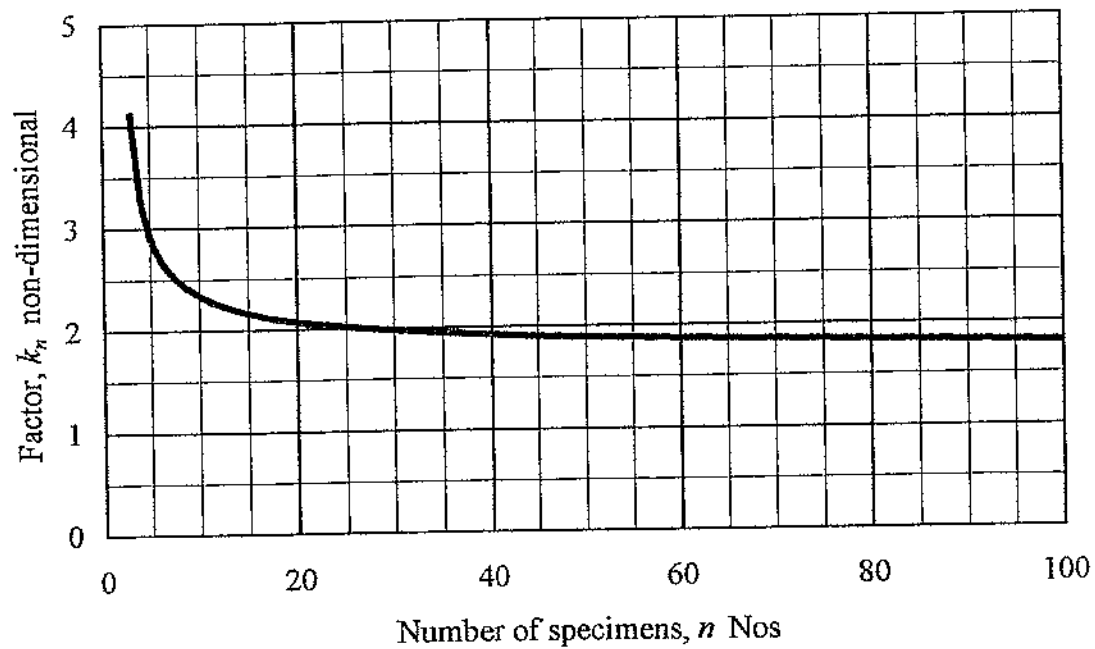


Figure 1. The factor  $k_n$  versus the number of observations  $n$ .

EXAMPLE 1. The following compressive strengths have been determined by means of the pull-out test method (CAPO-test) from one inspection section:

27.5 25.0 24.5 25.0 22.5 24.0 25.5 28.5 25.0 30.0 MPa

Calculation of the lower characteristic value (5 % fractile) is carried out in the following way, applying a spreadsheet, cf. table 2:

	Compressive strength, $f_c$ MPa	$\ln f_c$
$f_{c1}$	27.5	3.14186
$f_{c2}$	25.0	3.21888
$f_{c3}$	24.5	3.19867
$f_{c4}$	25.0	3.21889
$f_{c5}$	22.5	3.11352
$f_{c6}$	24.0	3.17805
$f_{c7}$	25.5	3.23868
$f_{c8}$	28.5	3.34990
$f_{c9}$	25.0	3.21888
$f_{c10}$	30.0	3.40120
Mean value	25.75	3.24508
Standard deviation	2.252	0,08576
Coefficient of variation	0.087	--
Lower characteristic value	21.00	--

Table 2. Calculation of the lower characteristic value of observed compressive strength.

In Table 2 the mean value and the standard deviations of the logarithms of the compressive strengths are determined as  $M_{\ln f} = 3.24508$  and  $S_{\ln f} = 0.08576$  respectively. Thus, the lower characteristic value (5 % fractile) yields:

$$f_k = \exp(M_{\ln f} - k_n \times S_{\ln f}) = \exp(3.24508 - 2.34 \times 0.08576) = 21.00 \text{ MPa}$$

**EXAMPLE 2.** In a 450 m<sup>2</sup> overlay casting the following values of pull-off strengths were determined using 75 mm diameter dollies:

1.85 1.91 1.56 1.42 1.88 1.69 MPa

Calculation of the lower characteristic value (5 % fractile) is carried out in the following way, applying a spreadsheet, cf. table 3:

	Pull-off strength, $f_i$ MPa	$\ln f_i$
$f_{i1}$	1.85	0.6152
$f_{i2}$	1.91	0.6471
$f_{i3}$	1.56	0.4447
$f_{i4}$	1.42	0.3507
$f_{i5}$	1.88	0.6313
$f_{i6}$	1.69	0.5247
Mean value	1.718	0.5356
Standard deviation	0.198	0.1187
Coefficient of variation	11.5 %	—
Lower characteristic value	1.24	—

Table 3. Calculation of the characteristic value of observed pull-off strength.

In Table 3 the mean value and the standard deviations of the logarithms of the pull-off strengths are determined as  $M_{\ln f} = 0.5356$  and  $S_{\ln f} = 0.1187$  respectively. Thus, the lower characteristic value (5 % fractile) yields:

$$f_{ik} = \exp(M_{\ln f} - k_n \times S_{\ln f}) = \exp(0.5356 - 2.70 \times 0.1187) = 1.24 \text{ MPa}$$